

ISSN 2518-1491 (Online),
ISSN 2224-5286 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ

Д.В.Сокольский атындағы «Жанармай,
катализ және электрохимия институты» АҚ

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
АО «Институт топлива, катализа и
электрохимии им. Д.В. Сокольского»

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
JSC «D.V. Sokolsky institute of fuel, catalysis
and electrochemistry»

SERIES
CHEMISTRY AND TECHNOLOGY

2 (434)

MARCH - APRIL 2019

PUBLISHED SINCE JANUARY 1947

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of chemistry and technologies scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of chemistry and technologies in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of chemical sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Химия және технология сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Химия және технология сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді химиялық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия химии и технологий» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по химическим наукам для нашего сообщества.

Б а с р е д а к т о р ы
х.ғ.д., проф., ҚР ҰҒА академигі **М.Ж. Жұрынов**

Р е д а к ц и я а л қ а с ы:

Ағабеков В.Е. проф., академик (Белорус)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Ресей)
Газалиев А.М. проф., академик (Қазақстан)
Ергожин Е.Е. проф., академик (Қазақстан)
Жармағамбетова А.К. проф. (Қазақстан), бас ред. орынбасары
Жоробекова Ш.Ж. проф., академик (Қырғыстан)
Иткулова Ш.С. проф. (Қазақстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Қазақстан)
Баешов А.Б. проф., академик (Қазақстан)
Бүркітбаев М.М. проф., академик (Қазақстан)
Джусипбеков У.Ж. проф. корр.-мүшесі (Қазақстан)
Молдахметов М.З. проф., академик (Қазақстан)
Мансуров З.А. проф. (Қазақстан)
Наурызбаев М.К. проф. (Қазақстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Қазақстан)
Стрельцов Е. проф. (Белорус)
Тәшімов Л.Т. проф., академик (Қазақстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Тәжікстан)
Фарзалиев В. проф., академик (Әзірбайжан)

«ҚР ҰҒА Хабарлары. Химия және технология сериясы».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» Республикалық қоғамдық бірлестігі (Алматы қ.)

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №1089-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://chemistry-technology.kz/index.php/en/arithiv>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2019

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д.х.н., проф., академик НАН РК **М. Ж. Журинов**

Р е д а к ц и о н н а я к о л л е г и я:

Агабеков В.Е. проф., академик (Беларусь)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Россия)
Газалиев А.М. проф., академик (Казахстан)
Ергожин Е.Е. проф., академик (Казахстан)
Жармагамбетова А.К. проф. (Казахстан), зам. гл. ред.
Жоробекова Ш.Ж. проф., академик (Кыргызстан)
Иткулова Ш.С. проф. (Казахстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Казахстан)
Баешов А.Б. проф., академик (Казахстан)
Буркитбаев М.М. проф., академик (Казахстан)
Джусипбеков У.Ж. проф. чл.-корр. (Казахстан)
Мулдахметов М.З. проф., академик (Казахстан)
Мансуров З.А. проф. (Казахстан)
Наурызбаев М.К. проф. (Казахстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Казахстан)
Стрельцов Е. проф. (Беларусь)
Ташимов Л.Т. проф., академик (Казахстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Гаджикистан)
Фарзалиев В. проф., академик (Азербайджан)

«Известия НАН РК. Серия химии и технологии».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10893-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел. 272-13-19, 272-13-18,
<http://chemistry-technology.kz/index.php/en/arhiv>

© Национальная академия наук Республики Казахстан, 2019

Адрес редакции: 050100, г. Алматы, ул. Кунаева, 142,
Институт органического катализа и электрохимии им. Д. В. Сокольского,
каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

E d i t o r i n c h i e fdoctor of chemistry, professor, academician of NAS RK **M.Zh. Zhurinov****E d i t o r i a l b o a r d:**

Agabekov V.Ye. prof., academician (Belarus)
Volkov S.V. prof., academician (Ukraine)
Vorotyntsev M.A. prof., academician (Russia)
Gazaliyev A.M. prof., academician (Kazakhstan)
Yergozhin Ye.Ye. prof., academician (Kazakhstan)
Zharmagambetova A.K. prof. (Kazakhstan), deputy editor in chief
Zhorobekova Sh.Zh. prof., academician (Kyrgyzstan)
Itkulova Sh.S. prof. (Kazakhstan)
Mantashyan A.A. prof., academician (Armenia)
Praliyev K.D. prof., academician (Kazakhstan)
Bayeshov A.B. prof., academician (Kazakhstan)
Burkitbayev M.M. prof., academician (Kazakhstan)
Dzhusipbekov U.Zh. prof., corr. member (Kazakhstan)
Muldakhmetov M.Z. prof., academician (Kazakhstan)
Mansurov Z.A. prof. (Kazakhstan)
Nauryzbayev M.K. prof. (Kazakhstan)
Rudik V. prof., academician (Moldova)
Rakhimov K.D. prof., academician (Kazakhstan)
Streltsov Ye. prof. (Belarus)
Tashimov L.T. prof., academician (Kazakhstan)
Toderash I. prof., academician (Moldova)
Khalikov D.Kh. prof., academician (Tadjikistan)
Farzaliyev V. prof., academician (Azerbaijan)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of chemistry and technology.
ISSN 2518-1491 (Online),
ISSN 2224-5286 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of Information and Archives of the Ministry of Culture and Information of the Republic of Kazakhstan N 10893-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,

<http://chemistry-technology.kz/index.php/en/arhiv>

© National Academy of Sciences of the Republic of Kazakhstan, 2019

Editorial address: Institute of Organic Catalysis and Electrochemistry named after D. V. Sokolsky
142, Kunayev str., of. 310, Almaty, 050100, tel. 291-62-80, fax 291-57-22,
e-mail: orgcat@nursat.kz

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES CHEMISTRY AND TECHNOLOGY

ISSN 2224-5286

<https://doi.org/10.32014/2019.2518-1491.21>

Volume 2, Number 434 (2019), 66 – 72

UDK 544.6:546.82

SRSTI 31.15.33

A.B. Bayeshov¹, R.N. Nurdillayeva², Sh.H. Khabibullayeva²

¹«D.V.Sokolsky Institute of Fuel, Catalysis and Electrochemistry», Almaty, Kazakhstan;

²Khoja Akhmet Yassawi International Kazakh-Turkish University, Turkistan, Kazakhstan
bayeshov@mail.ru, raushan.nurdillayev@ayu.edu.kz, shakhista.khabibullayeva@ayu.edu.kz

**EFFECT OF THE BROMIDE IONS ON THE TITANIUM
ELECTRODE DISSOLUTION POLARIZED BY ALTERNATING
CURRENT IN AQUEOUS SOLUTIONS**

Abstract. The titanium electrode dissolution possibility polarized by industrial alternating current (AC) with 50 Hz frequency in potassium bromide aqueous solution acidified by sulfuric acid was shown for the first time and the process dissolving titanium were determined. The influence of alternating current density (200-1200 A/m²), potassium bromide solution concentration (1.0-5.0 M) and sulfuric acid concentration (0.5-4.0 M), AC frequency (25-150 Hz), electrolyte temperature (25-80°C) and electrolysis duration (0.5-2 hours) on the current efficiency (CE) of the titanium dissolution were considered. It was observed extremely low CE (1.8%) of the titanium dissolution by polarization anodic direct current. When titanium was polarized by alternating current, the CE reached 60% at a current density of 200 A/m² in the titanium electrode, and as the current density was increased the CE of titanium dissolution was decreased. The titanium dissolution CE showed the maximum value in 0.5 M sulfuric acid and 1.0 M potassium bromide solution. The decrease of titanium electrode CE due to the increase of the electrolysis duration and the AC frequency effect was determined.

Keywords: titanium, alternating current, electrolysis, potassium bromide, sulfuric acid.

Today the application of industrial alternating current frequency of 50 Hz to the electrolysis processes in the field of applied electrochemistry contributes to the new scientific trends development. This method allows conducting electrochemical reactions in solutions, dissolving insoluble metals and activating these processes [1-4].

Titanium and its compounds are light, biologically harmless and resistant to corrosion and environmental impacts. Though this metal is one and a half times heavier than aluminum, two times lighter than iron, it is widely used for the production of aircraft engines, orthopedic implants, construction materials, submarines, electrode and pyrotechnics due to its six times stronger solidity [5-7]. Titanium dioxide has a great deal to contribute to the food industry as an additive labeled E171. Titanium (III) nitride is a unique compound in covering metal surfaces, also known as fake gold, which is resistant to the decays king's water and is much cheaper than gold [8].

Titanium is an element with high melting point that is not soluble in acids by chemical methods. Due to its wide use today, obtaining various compounds through its dissolution is of great importance [9].

Titanium dissolution in hydrochloric acid with fluoride ions and in phosphoric acid solution in the presence of industrial alternating current has been shown in scientific works [10-15]. However, the works do not specify the electrochemical properties of titanium electrode in the bromide aqueous media [16-20]. In this regard, the present work considered the electrochemical dissolution behavior of titanium electrode in bromide aqueous media. In addition, the influence of the main parameters (current density, electrolyte temperature and solution concentration, alternating current frequency, etc.) on electrochemical dissolution process of titanium electrode was investigated.

Results and discussion

The preliminary experiments results showed the insolubility of the two titanium plates in bromide aqueous solutions in the presence of direct current as their surface was covered by a layer of oxide film. However, when the two titanium electrodes were polarized with industrial alternating current, intensive dissolution of the metal was observed.

The current density effect on the titanium electrode dissolution in bromide aqueous solution was investigated (Table 1). The research results showed that the current efficiency reached 60% at a current density of 200 A/m² in the titanium electrode, but while the current density was increased the CE of titanium dissolution was decreased. This phenomenon can be explained with the oxide film formation on the titanium surface in the anodic half period of the alternating current at high current densities and these inherent oxide films could lead to passivation of electrode surface.

Table 1 - The influence of Current density on titanium electrodes polarized by alternating current on the CE of their dissolution

[KBr]=1,0 M, [H₂SO₄]=0,5 M, $\tau=0,5$ h

$i, A/m^2$	200	400	600	800	1000	1200
CE, %	60	41.6	28.2	22.4	18.3	14.7

The potassium bromide concentration effect in the absence of acid in the neutral medium was investigated to determine the titanium dissolution specificity in bromide aqueous solutions (see Table 2). The results showed the current efficiency decrease of the titanium electrode dissolution from 25% to 8% due to the increase of the potassium bromide concentration in the range of 1.0-5.0 M.

Table 2 - The effect of Potassium bromide concentration on the CE of titanium electrodes dissolution rate polarized by alternating current

$i = 200 A/m^2, \tau = 0.5$ h

[KBr], M	1	2	3	4	5
CE, %	25	17.2	13.4	10	8

Due to the low current efficiency of titanium dissolution in bromide aqueous solutions, it was investigated the titanium dissolution specificity in the presence of sulfuric acid (Table 3). With the increasing sulfuric acid concentration from 0.5M to 2.0 M there was observed dynamically increase of titanium dissolution current efficiency value from 12% to 44%. Further increase of sulfuric acid concentration leads to the current efficiency decrease up to 16%. This phenomenon can be assumed that sulfate ions first interact with the film on the titanium surface and create a favourable condition for the titanium dissolution. Further, the increase of oxygen-containing sulfate ions concentration simplifies the oxide film formation on the titanium surface and allows its passivation.

Table 3 - The effect of Sulfuric acid concentration on the CE of titanium electrodes dissolution rate polarized by alternating current

$i = 200 A/m^2, \tau = 0.5$ h

[KBr], M	0.5	1	2	3	4
CE, %	12	24.5	44	29.6	16

As the current efficiency of alternating current polarized titanium electrode did not exceed 44% in sulfuric acid, the potassium bromide solution was acidified with sulfuric acid 0.5 M and the potassium bromide concentration effect on the solution was investigated (Figure 1). The more the potassium bromide concentration was increased, the less the current efficiency decreased. This phenomenon can be explained

by the fact that initially when 1.0 M potassium bromide solution acidified with 0.5 M sulfuric acid, these acidified bromide ions created condition for titanium dissolving, but further increasing the potassium bromide concentration leads to the increase of bromide ions amount as a result of which the titanium passivation takes place. In this case, as the potassium bromide concentration effect (Table 2) is considered, a straight line decrease of the current efficiency value was observed. However, it should be noted that current efficiency increased by 2.5 times.

With a view to further increasing the titanium electrode current efficiency, the potassium bromide was acidified with sulfuric acid and the change in its concentration was investigated (Figure 2).

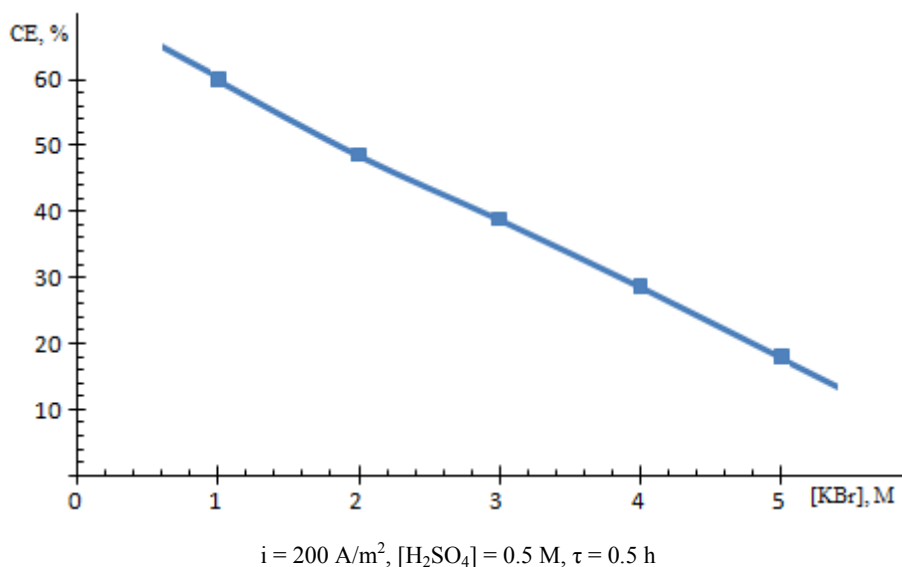


Figure 1 - The influence of Potassium bromide concentration on the CE of titanium electrodes dissolution polarized by alternating current

However, if an sharply fluctuate in a peak was observed in the sulfuric acid concentration, a straight line decrease in the titanium current efficiency took place when the potassium bromide solution was acidified with sulfuric acid solution and the sulfuric acid concentration was increased. The titanium electrode current efficiency decreased from 60% up to 18%.

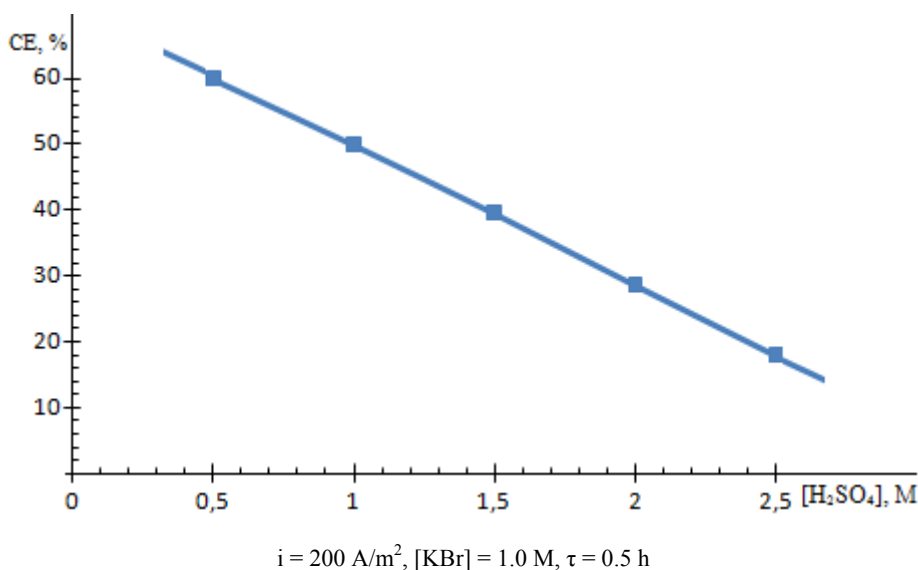


Figure 2 - The effect of Sulfuric acid concentration on the CE of titanium electrodes dissolution polarized by alternating current

The temperature effect on titanium electrode dissolution in bromide-acid aqueous solutions was considered (Figure 3). Studies have shown the current efficiency decrease of titanium electrode dissolution due to the temperature increase. According to the fundamental principles, the increase of solution temperature should cause the increase of chemical reactions rate. Explaining the abnormal decrease in the titanium electrode dissolution rate due to the temperature increase requires additional studies. It is possible to assume that as the solution temperature increases, the oxide film stability on the titanium surface increases.

The temperature effect on the current efficiency of alternating current polarized titanium electrode was investigated from 25°C up to 80°C. It should be noted that temperature increase lead to downward trend and the titanium current efficiency decreased from 60 to 24%.

Following figure 4 shows the electrolysis duration effect on the current efficiency of alternating current polarized titanium electrode. The current efficiency of titanium electrode decreased from 60% to 20% between 0.5-2.0 hours. As we have seen, as the electrolysis time was increased, the current efficiency firstly increased and then decreased. The bromide ions reacted with the oxide film on the titanium surface and created a complete titanium dissolution. As the time passed, the dissolved titanium slowed down by forming oxide film again on the electrode surface.

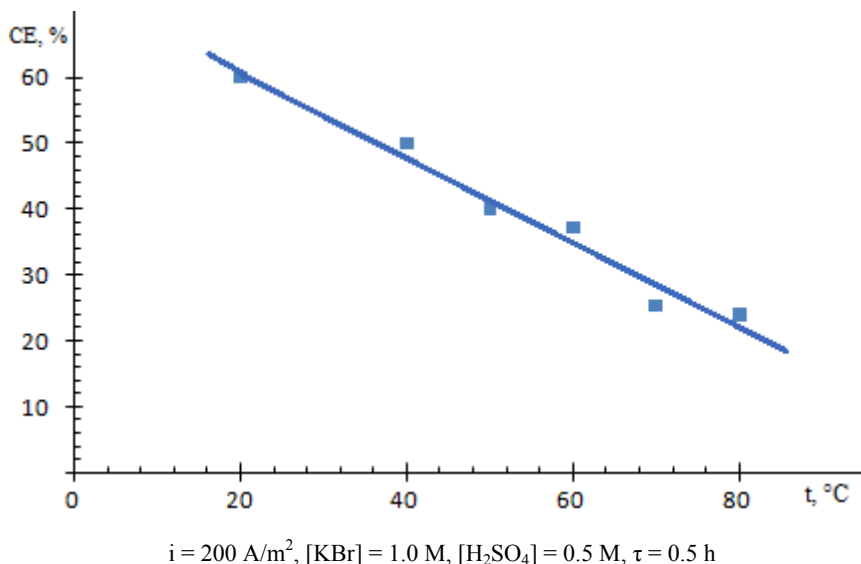


Figure 3 - The influence of temperature in the CE of titanium electrodes dissolution polarized by alternating current

The current frequency effect on the titanium electrode dissolution in bromide-acid aqueous solutions is given in Figure 5. Experimental data have shown that as the current efficiency rate is increased from 25 to 150 Hz, the titanium dissolution current efficiency increases up to 50 Hz and then gradually decreases. This change can be assumed that the more the current frequency increases, the better rational condition is created for the oxygen shell formation on the surface of the alternating current polarized titanium electrode.

The titanium electrode dissolution in bromide-acid aqueous solutions showed a decrease in the current efficiency from 60% to 25% between 50 - 150 Hz.

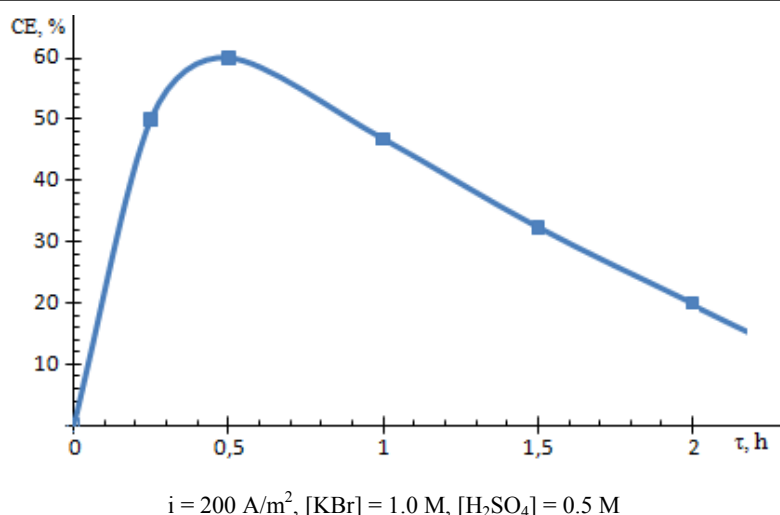


Figure 4 - The effect of electrolysis duration on the CE of titanium electrodes dissolution polarized by alternating current

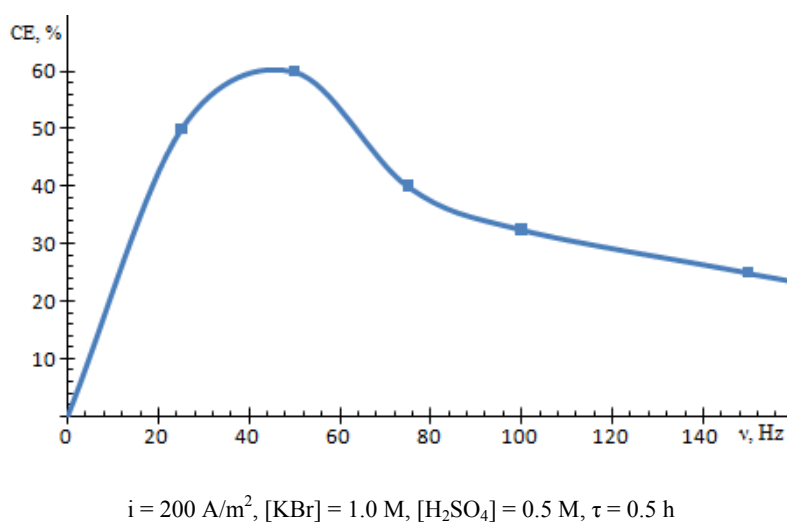


Figure 5 - The influence of current frequency on current efficiency of titanium electrodes dissolution polarized by alternating current

In conclusion, titanium electrode dissolution polarized by alternating current in bromide aqueous solutions was shown for the first time. The various parameters influence on the titanium dissolution rate was investigated. It has been found that titanium dissolution current efficiency reached 60% in effective conditions of electrolysis. The results of this study allow dissolving the insoluble titanium electrode in bromide acid solutions and producing technologies for obtaining its various compounds.

ӘОЖ 544.6:546.82
МРНТИ 31.15.33

А.Б. Баешов ¹, Р.Н. Нүрділлаева ², Ш.Х. Хабибуллаева ²

¹Д.В.Сокольский атындағы Жанармай, катализ және электрохимия институты, Алматы;

²Қожа Ахмет Ясауи атындағы Халықаралық қазақ-түрік университеті, Түркістан

АЙНЫМАЛЫ ТОКПЕН ПОЛЯРИЗАЦИЯЛАНҒАН ТИТАН ЭЛЕКТРОДЫНЫҢ СУЛЫ ЕРІТІНДІЛЕРДЕ ЕРУІНЕ БРОМИД ИОНДАРЫНЫҢ ӘСЕРІ

Аннотация. Ұсынылып отырған жұмыста күкірт қышқылымен қышқылданған калий бромиді ерітіндісінде жиілігі 50 Гц өндірістік айнымалы токпен поляризацияланған титан электродының еритіндігі алғаш рет

көрсетілді және еру заңдылықтары анықталды. Титанның еруінің ток бойынша шығымына айнымалы ток тығыздығының (200-1200 А/м²), калий бромиді ерітіндісі концентрациясының (1,0-5,0 М), күкірт қышқылы концентрациясының (0,5-4,0 М), айнымалы ток жиілігінің (25-150 Гц), ерітінді температурасының (25-80 °С), электролиз ұзақтығының (0,5-2 сағат) әсерлері қарастырылды. Тұрақты токпен поляризацияланғанда титанның өте төмен ток бойынша шығыммен ерітіндігі байқалды (1,8%). Айнымалы токпен поляризацияланғанда титан электродындағы ток тығыздығы 200 А/м² кезінде ток бойынша шығым 60% тең болды да, ток тығыздығын жоғарылатқан сайын оның еруінің ТШ төмендегендігі анықталды. Титан еруінің ток бойынша шығымы 0,5 М күкірт қышқылы және 1,0 М калий бромиді ерітіндісінде максималды мәнді көрсетті. Электролиз ұзақтығының және айнымалы ток жиілігінің әсерін арттырған сайын титан электродының ток бойынша шығымы төмендейтіндігі анықталды.

Түйін сөздер: титан, айнымалы ток, электролиз, калий бромиді, күкірт қышқылы.

УДК 544.6:546.82
МРНТИ 31.15.33

А.Б. Баешов¹, Р.Н. Нурдиллаева², Ш.Х. Хабибуллаева²

¹АО «Институт топлива, катализа и электрохимии им. Д.В.Сокольского», Алматы

²Международный казахско-турецкий университет им. Ходжи Ахмеда Ясави, Туркестан

ВЛИЯНИЕ БРОМИД-ИОНОВ НА РАСТВОРЕНИЕ ТИТАНОВЫХ ЭЛЕКТРОДОВ В ВОДНОМ РАСТВОРЕ ПРИ ПОЛЯРИЗАЦИИ ПЕРЕМЕННЫМ ТОКОМ

Аннотация. В данной работе впервые показана возможность растворения титана в сернокислых бромидных растворах при поляризации промышленным переменным током частотой 50 Гц и установлены протекания процесса закономерности растворения титана. Изучено влияние – плотности переменного тока (200-1200 А/м²), концентрации раствора бромида калия (1,0-5,0 М), концентрации серной кислоты (0,5-4,0 М), частоты переменного тока (25-150 Гц), температуры раствора (25-80 °С) и продолжительности электролиза (0,5-2 часа) на выход по току (ВТ) растворения титана. При поляризации анодным постоянным током наблюдалась низкий ВТ растворения титана (1,8%). А при поляризации титана переменным током, при плотности тока 200 А/м² ВТ составил 60 %, а с увеличением плотности тока ВТ растворения титанового электрода уменьшается. Установлено, что в растворе, содержащем 1,0 М бромистого калия и 0,5 М серной кислоты наблюдается максимальное значение ВТ растворения титанового электрода. При увеличении продолжительности электролиза и частоты переменного тока ВТ растворения титана уменьшается.

Ключевые слова: титан, переменный ток, электролиз, бромид калия, серная кислота.

Information about authors:

A.B. Bayeshov – «D.V.Sokolsky Institute of Fuel, Catalysis and Electrochemistry», Doctor of Chemistry Science, Professor, bayeshov@mail.ru, the author made a critical review of important intellectual content and approved the final version of the article before submitting it for publication.

R.N. Nurdillayeva – Khoja Akhmet Yassawi International Kazakh-Turkish University, Candidate of Chemistry Science, Associate Professor raushan.nurdillayev@ayu.edu.kz, the author made a significant contribution to the concept and design of the study, data acquisition and interpretation, and also made a critical review on the subject of important intellectual content.

Sh.H. Khabibullayeva – Khoja Akhmet Yassawi International Kazakh-Turkish University, master degree, II course, shakhista.khabibullayeva@ayu.edu.kz, the author made a significant contribution to the concept and design of the study, data acquisition and interpretation.

REFERENCES

- [1] Andreev J. (2016) Electrochemistry of metals and alloys. [Elektrokhimiya metallov i splavov]. Moscow, Russia. 326 p. ISBN: 978-5-94084-044-2 (In Russian).
- [2] Baeshov A.B., Baeshova A.K., Baeshova C.A. (2014). Electrochemistry (theory and practice). [Elektrokhimiya (teoriyasi men koldaniui)]. Almaty: Kazakh university. ISBN 978-601-04-0671-1. 316 p. (In Kazakh).
- [3] Baeshov A.B., Nurdillayeva R.N., Tashkenbayeva N.Zh., Ozler M.A. (2018) // Dissolution of stainless steel under alternating current polarization. NEWS of the academy of sciences of the Republic of Kazakhstan. ISSN 2518-1491. Almaty. 46-52. (In Eng).
- [4] Baeshov A.B., Nurdillayeva R.N., Tashkenbayeva N.Zh. (2018) // Dissolution of stainless steel polarized by alternating current in hydrochloric acid solutions. Izvestiya NAN RK. (In Eng).
- [5] Gospodinov D., Nikolay F., Dimitrov S. (2016) // Classification, properties and application of titanium and its alloys. Proceedings of university of ruse. Volume 55, book 2 (In Eng).
- [6] Leyens C., Peters M. (2003). Titanium and Titanium Alloys. Fundamentals and Applications. Edited by Christoph Leyens, Manfred Peters Copyright. WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim ISBN: 3-527-30534-3. (In Eng).
- [7] Larica B.R., Iara A.O., Sebastião E.K., Carlos Alberto D.R., Thaís P.B., Eduardo B. (2015) // Effects of Peracetic Acid on the Corrosion Resistance of Commercially Pure Titanium. Brazilian Dental Journal. 660-666 (In Eng).

[8] Shlyamenov A.P. et al. (2000) Corrosion-resistant, heat-resistant and high-resistant steel and alloys. [Korroziionnostoykiye, zhrostoykiye i vysokoprochnyye stali i splavy]. Moscow, Russia. ISBN 5-89594-028-5 (In Russian).

[9] Zameletdinov I.I. (2007) Corrosion and protection of metals. [Korroziya i zashchita metallov]. Perm: Publishing house of Perm State Technical University. ISBN: 9785881518332. (In Russian).

[10] Erubaev E.A. (2017) Cyclic deformation and thermomechanical stability of titanium and its alloys for medical purpose. [Ciklicheskaja deformacija i termomechanicheskaja stabil'nost' titana i ego splavov medicinskogo naznacheniya]. Dissertation. Belgorod, Russia. (In Russian).

[11] Baeshov A.B., Sapieva M.M. (2014) // Electrochemical behaviour of titanium electrodes at polarization by industrial alternating current in phosphoric solution containing fluoride ions. [Ondiristik ajnymaly tokpen poljarizacijalangan titan elektrodтарынын фторид иондары бар тұз қышқылында еруі]. Almaty: Izvestija NAN RK. 7-10. (In Kazakh).

[12] Baeshov A.B., Baeshova A.K., Dauletbaev A. (2010) Method for producing tetravalent titanium sulphate. [Sposob polucheniya sul'fata chetyrehvalentogo titana]. [Innovation patent of Republic of Kazakhstan] №22790 ot 19.05.09 Bulletin №8. (In Russian).

[13] Baeshov A.B., Iztileuov G.M., Zhurinov M.Zh. (2007) // Investigation of dissolution of titanium in titanium-graphite system in aqueous solutions. [Ondiristik ajnymaly tokpen poljarizacijalangan titannyn kuramynda fторид иондары бар фосфор қышқылы еритіндісіндегі электрохимиялық кәсіпті]. Committee of science. RGP "Institute of Organic Catalysis and Electrochemistry named D.V. Sokolskiy". 75. (In Kazakh).

[14] Davydova A.D., Kabanova T.B., Volgin V.M. (2017) // Electrochemical Machining of Titanium. Russian Journal of Electrochemistry. 1056–1072. (In Eng).

[15] Gnedonov S.V., Sinebrjuhov S.L., Egorkin V.S., Mashtaljar D.V., Legostaeva E.V., Sharkeev Ju.P. (2011) // Electrochemical properties of nanostructured titanium. [Elektrohimicheskie svoystva nanostrukturirovannogo titana]. Vestnik DVO RAN. 24-29. (In Russian).

[16] Sarbaeva G.T., Baeshov A.B., Sarbaeva M.T., Sarbaeva Q.T. (2009) // The dissolution of the polarized titanium electrode with the three-phase AC in the nitrogenic acid solution. [Ush fazaly ajnymaly tokpen poljarizacijalangan titan elektrodynyn azot қышқылы еритіндісінде еруі]. Izvestiya NAN RK. 34-37. (In Kazakh).

[17] Baeshov A.B., Baeshova A.K., Sarbaeva G.T. (2010) // Method for producing tetravalent titanium chloride. [Sposob polucheniya chlorida chetyrehvalentnogo titana]. [Innovation patent of Republic of Kazakhstan] №22762 ot 24.06.09 Bulletin №8. (In Russian).

[18] Popova S.S., Kovalchuk Yu.A. (2010) // Electrochemical behavior of titanium in $\text{Li}_3\text{HO}_2(\text{P}_0_4)_3$ solutions. [Elektrohimicheskoe povedenie titana v rastvorah $\text{Li}_3\text{HO}_2(\text{P}_0_4)_3$]. Vestnik SGU. 101-104. (In Russian).

[19] Spiridonov B.A. (2017) // The study of the electrochemical behaviour of titanium in various environments. [Issledovanie elektrohimicheskogo povedeniya titana v razlichnyh sredah. Sovremennye tendencii razvitiya nauki i tehnologii]. Modern trends in the development of science and technology. Belgorod. 71-73. ISSN: 2413-0869 (In Russian).

[20] Frayret C., Botella Ph., Jaszay Th., Delville M.H. (2004) // Titanium Dissolution-Passivation in Highly Chloridic and Oxygenated Aqueous Solutions. Journal of the The Electrochemical Society. 543-550. ISSN: 0013-4651 (In Eng).

[21] Bayeshov A.B., Myrzabekov B.E., Kolesnikov A.V. PATTERNS OF FORMATION OF DISPERSED COPPER POWDERS IN THE BODY OF ELECTROLYTE DURING THE USE OF COPPER ANODE IN SULFURIC ACID SOLUTION ALONG WITH TITANIUM (IV) IONS IN THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN SERIES CHEMISTRY AND TECHNOLOGY ISSN 2224-5286 <https://doi.org/10.32014/2018.2518-1491.31> Volume 6, Number 432 (2018), 96–101.

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации
в журнале смотреть на сайте:

www.nauka-nanrk.kz

<http://chemistry-technology.kz/index.php/en/arhiv>

ISSN 2518-1491 (Online), ISSN 2224-5286 (Print)

Редакторы: *М. С. Ахметова, Т. А. Апендиев, Аленов Д. С.*
Верстка на компьютере *А. М. Кульгинбаевой*

Подписано в печать 04.04.2019.
Формат 60x881/8. Бумага офсетная. Печать – ризограф.
4 п.л. Тираж 300. Заказ 2.