

**ISSN 2518-1491 (Online),
ISSN 2224-5286 (Print)**

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ГЫЛЫМ АКАДЕМИЯСЫНЫҢ

Д.В.Сокольский атындағы «Жанармай,
катализ және электрохимия институты» АҚ

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
АО «Институт топлива, катализа и
электрохимии им. Д.В. Сокольского»

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
JSC «D.V. Sokolsky institute of fuel, catalysis
and electrochemistry»

**SERIES
CHEMISTRY AND TECHNOLOGY**

4 (436)

JULY-AUGUST 2019

PUBLISHED SINCE JANUARY 1947

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of chemistry and technologies scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of chemistry and technologies in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of chemical sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Химия және технология сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруды. Web of Science зерттеушілер, авторлар, баспашилар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Химия және технология сериясы Emerging Sources Citation Index-ке енүі біздің қоғамдастық үшін ең өзекті және беделді химиялық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия химии и технологий» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по химическим наукам для нашего сообщества.

Бас редакторы
х.ғ.д., проф., ҚР ҮҒА академигі М.Ж. Жұрынов

Редакция алқасы:

Агабеков В.Е. проф., академик (Белорус)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Ресей)
Газалиев А.М. проф., академик (Қазақстан)
Ергожин Е.Е. проф., академик (Қазақстан)
Жармағамбетова А.К. проф. (Қазақстан), бас ред. орынбасары
Жоробекова Ш.Ж. проф., академик (Қырғыстан)
Иткулова Ш.С. проф. (Қазақстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Қазақстан)
Баешов А.Б. проф., академик (Қазақстан)
Бұркітбаев М.М. проф., академик (Қазақстан)
Джусипбеков У.Ж. проф. корр.-мүшесі (Қазақстан)
Молдахметов М.З. проф., академик (Қазақстан)
Мансуров З.А. проф. (Қазақстан)
Наурызбаев М.К. проф. (Қазақстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Қазақстан)
Стрельцов Е. проф. (Белорус)
Тәшімов Л.Т. проф., академик (Қазақстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Тәжікстан)
Фарзалиев В. проф., академик (Әзірбайжан)

«ҚР ҮҒА Хабарлары. Химия және технология сериясы».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Меншіктенуші: «Қазақстан Республикасының Үлттық ғылым академиясы» Республикалық қоғамдық бірлестігі (Алматы қ.)

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №1089-Ж мерзімдік басылым тіркеуіне қойылу туралы күзелік

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://chemistry-technology.kz/index.php/en/archiv>

© Қазақстан Республикасының Үлттық ғылым академиясы, 2019

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д.х.н., проф.,академик НАН РК **М. Ж. Журинов**

Р е д а к ц и о н на я к ол л е г и я:

Агабеков В.Е. проф., академик (Беларусь)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Россия)
Газалиев А.М. проф., академик (Казахстан)
Ергожин Е.Е. проф., академик (Казахстан)
Жармагамбетова А.К. проф. (Казахстан), зам. гл. ред.
Жоробекова Ш.Ж. проф., академик (Кыргызстан)
Иткулова Ш.С. проф. (Казахстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Казахстан)
Баешов А.Б. проф., академик (Казахстан)
Буркитбаев М.М. проф., академик (Казахстан)
Джусипбеков У.Ж. проф. чл.-корр. (Казахстан)
Мулдахметов М.З. проф., академик (Казахстан)
Мансуров З.А. проф. (Казахстан)
Наурызбаев М.К. проф. (Казахстан)
Рудик В. проф.,академик (Молдова)
Рахимов К.Д. проф. академик (Казахстан)
Стрельцов Е. проф. (Беларусь)
Ташимов Л.Т. проф., академик (Казахстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Таджикистан)
Фарзалиев В. проф., академик (Азербайджан)

«Известия НАН РК. Серия химии и технологии».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10893-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел. 272-13-19, 272-13-18,

<http://chemistry-technology.kz/index.php/en/arhiv>

© Национальная академия наук Республики Казахстан, 2019

Адрес редакции: 050100, г. Алматы, ул. Кунаева, 142,
Институт органического катализа и электрохимии им. Д. В. Сокольского,
каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

Editor in chief
doctor of chemistry, professor, academician of NAS RK **M.Zh. Zhurinov**

Editorial board:

Agabekov V.Ye. prof., academician (Belarus)
Volkov S.V. prof., academician (Ukraine)
Vorotyntsev M.A. prof., academician (Russia)
Gazaliyev A.M. prof., academician (Kazakhstan)
Yergozhin Ye.Ye. prof., academician (Kazakhstan)
Zharmagambetova A.K. prof. (Kazakhstan), deputy editor in chief
Zhorobekova Sh.Zh. prof., academician (Kyrgyzstan)
Itkulova Sh.S. prof. (Kazakhstan)
Mantashyan A.A. prof., academician (Armenia)
Praliyev K.D. prof., academician (Kazakhstan)
Bayeshov A.B. prof., academician (Kazakhstan)
Burkitbayev M.M. prof., academician (Kazakhstan)
Dzhusipbekov U.Zh. prof., corr. member (Kazakhstan)
Muldakhmetov M.Z. prof., academician (Kazakhstan)
Mansurov Z.A. prof. (Kazakhstan)
Nauryzbayev M.K. prof. (Kazakhstan)
Rudik V. prof., academician (Moldova)
Rakhimov K.D. prof., academician (Kazakhstan)
Streltsov Ye. prof. (Belarus)
Tashimov L.T. prof., academician (Kazakhstan)
Toderash I. prof., academician (Moldova)
Khalikov D.Kh. prof., academician (Tadzhikistan)
Farzaliyev V. prof., academician (Azerbaijan)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of chemistry and technology.
ISSN 2518-1491 (Online),
ISSN 2224-5286 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)
The certificate of registration of a periodic printed publication in the Committee of Information and Archives of the Ministry of Culture and Information of the Republic of Kazakhstan N 10893-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,
<http://chemistry-technology.kz/index.php/en/arhiv>

© National Academy of Sciences of the Republic of Kazakhstan, 2019

Editorial address: Institute of Organic Catalysis and Electrochemistry named after D. V. Sokolsky
142, Kunayev str., of. 310, Almaty, 050100, tel. 291-62-80, fax 291-57-22,
e-mail: orgcat@nursat.kz

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES CHEMISTRY AND TECHNOLOGY

ISSN 2224-5286

<https://doi.org/10.32014/2019.2518-1491.44>

Volume 4, Number 436 (2019), 60 – 65

UDC 549:622.775

R.A. Aubakirova¹, Zh.K. Shomanova², R.Z. Safarov³, E. Atasoy⁴

¹Sarsen Amanzholov East Kazakhstan State University, Ust-Kamenogorsk, Kazakhstan

²Pavlodar State Pedagogical University, Pavlodar, Kazakhstan

³L.N. Gumilyov Eurasian National University, Astana, Kazakhstan

⁴Uludag University, Bursa, Turkey

ANALYSIS OF COPPER-CONTAINING PRODUCTS FOR THE CONTENT OF NOBLE METALS

Abstract: In the article we are presenting the results of electron microscopy study of the samples of blister copper taken from copper production. It was shown significant amount of noble metals – silver and gold. As a result, silver was found in the range of 0.29-0.59%, gold – up to 0.66%. The method of assay-gravimetric detection of gold and silver in samples of blister copper is described.

Keywords: copper, noble metals, melting, gold, silver, electron microscopy, impurity.

Introduction

Kazakhstan is one of the largest producers of copper in the world meanwhile more than half of produced refined copper is exported. That is why copper as well as aluminum, nickel and ferrous metals are ones of the key export products. Exported copper is represented by copper concentrate, refined copper and copper wire rod.

Blister copper contains impurities, which deteriorate quality of copper (sulfur, oxygen et al.), and therefore to be removed, as well as impurities non-affecting the quality of copper, but extracted because of their value (silver and gold) [1-4].

In present time for determination of gold and silver content in samples of blister copper of copper production assay-gravimetric method of analysis is widely used [5-9]. Related to bulk up of copper production necessary of using more express method of analysis emerges not giving up by accuracy to assay-gravimetric method. Thus, the development and implementation of appropriate methods of blister copper analysis is an important issue.

Methods and materials

Normally used methods of assay-gravimetric detection of gold and silver in samples of blister copper are described, for example, in standards [10, 11].

The method is based on melting of blister copper samples with furnace charge containing lead (as a collector of noble metals) and borax as a flux at temperature of $1000\pm50^{\circ}\text{C}$. A lead bullion (werkblei, lead alloy containing silver and gold) and slug are obtained after sherber melting. Lead is separated from gold and silver by cupellation of alloy on cupel in muffle furnace at temperature of $950\pm50^{\circ}\text{C}$ with obtaining of gold-silver regulus. Gold is separated from silver by solvation of silver in nitric acid. Mass of silver is calculated as difference between mass of gold-silver regulus and mass of the gold.

The method is designed for identification of mass fraction of gold from 20 to 400 g./ton and silver from 500 to 12000 g./ton.

The sample of blister copper (5.00 g.) is weighed on precision (technical) scales, placed in a borax glazed sherber. Above the sample components of furnace charge are poured. The components are weighed on electronic scales, they contain 80 g. of granulated lead and 8 g. of borax.

Sherbering is carried on in the muffle furnace at a temperature of $1000\pm50^{\circ}\text{C}$. During sherbering oven door is slightly opened up for access of air oxygen. In the presence of oxygen, melt is oxidized and after interaction with borax it gives a slug, in which base-metal oxides move. The slug is shifted to sherber periphery, and melted lead forms center or «eye» of the melt. When lead «eye» will be covered with slug, the sherber stays in the muffle from five to 8 minutes and then melt is poured into a mould. Cooled lead alloy is separated from the slug, forged as a cube and cupelled.

Cupelling is carried on in the muffle furnace at a temperature of $950\pm50^{\circ}\text{C}$. Werkblei is placed in the muffle furnace onto a cupel with diameter from 35 to 42 mm. Preliminary heated muffle furnace stays with closed door from 2 to 3 minutes until complete melting of the werkblei. After disposal of last remains of lead that can be signed with fulguration, following darkening and solidification of reguluses, cupels are taken off from the furnace, cooled; reguluses are got off from the cupels using forceps, cleaned from adhered particles of cupel mass, flatten out on stithy obtaining thin plates and weighed on microscales. Obtained mass represents total mass of gold and silver. Golden-silver reguluses are parted.

Parting of reguluses is carried on on the electric stove. Solution of nitric acid ($\rho = 1.06 \text{ g/cm}^3$) is poured into the porcelain crucible filling it to three-quarters of volume. Then, crucibles are set on the stove and heated until emergence of bubbles. Flattened reguluses are placed into crucibles and solved until full solvation of silver not bringing the solution to a boil. After solvation, solution is drained into reservoir for collection of silver nitrate and hot solution of nitric acid ($\rho = 1.21 \text{ g/cm}^3$) is poured into the crucibles up to two thirds by volume. Crucibles are stood on the stove until full discontinuation of nitrogen oxides releasing. Then, the solution is also drained into a reservoir for collection of silver nitrate and gold beads are washed triple with hot water by decantation. Crucibles with gold beads are carefully dried on the stove and annealed in the muffle oven at a temperature of $550\pm50^{\circ}\text{C}$ for 5 minutes. After cooling gold bead is weighed on microscales. The difference between mass of golden-silver regulus and mass of gold bead is the mass of silver.

If the mass fraction of silver in the samples of blister copper is 600 g/ton or more, check sample is prepared from silver with mass corresponding to its mass fraction in the sample for taking into account silver loss after cupelling. For that samples of silver are placed into pockets of lead foil, compressed tightly and placed in the muffle oven on the cupels preliminary heated up to a temperature of $950\pm50^{\circ}\text{C}$. In the cupel along with the pocket the granulated lead is placed granulated in the amount at which total mass of lead with a mass of leaden pocket would correspond to mass of sample of werkblei obtained after sherber melting, and then it is cupelled.

Cupelling of check samples is carried on straight after analysis of the samples in the same muffle under the same conditions.

The values of metrological characteristics and standards for determining the mass fraction of gold must not exceed the values given in tables 1 and 2, respectively.

Table 1 - Numerical values of the limits
of the absolute error of silver content (g/ton)

Mass fraction of silver	Standard deviation of repeatability σ_r	Repeat limit at $n = 3$ r_3	Standard deviation of reproducibility σ_R	Reproducibility limit at $t = 2$ R	Limits of absolute error $\pm\Delta$
500 « 1000	10,6	35,0	15,2	42,0	30,0
1000 « 2000	21,1	70,0	30,0	83,0	59,0
2000 « 3000	30,2	100,0	43,3	120,0	85,0
3000 « 4000	45,3	150,0	65,0	180,0	128,0
4000 « 6000	60,4	200,0	86,6	240,0	170,0
6000 « 8000	75,5	250,0	108,3	300,0	213,0
8000 « 10000	90,6	300,0	130,0	360,0	256,0
10000 « 12000	105,7	350,0	151,6	420,0	298,0

Table 2 - Numerical values of the limits of the absolute error of gold content (g/ton)

Mass fraction of gold	Standard deviation of repeatability σ_r	Repeat limit at n = 3 r_3	Standard deviation of reproducibility σ_R	Reproducibility limit at t = 2 R	Limits of absolute error ±Δ
20 « 30	0,91	3,0	1,30	3,6	2,6
30 « 45	1,21	4,0	1,73	4,8	3,4
45 « 70	1,36	4,5	1,95	5,4	3,8
70 « 100	1,51	5,0	2,17	6,0	4,3
100 « 150	1,81	6,0	2,56	7,1	5,0
150 « 250	2,11	7,0	3,00	8,3	5,9
250 « 400	2,42	8,0	3,43	9,5	6,7

Results and discussion

The method of scanning electron microscopy is intended primarily for the study of the surface structure.

Scanning electron microscopes have 10^3 times greater depth of field than optical instruments, which provides a much higher image quality and allows you to successfully apply the technique of obtaining stereo pairs. The resulting images allow you to recreate a three-dimensional picture of the surface of the sample.

The scanning method allows for sequential analysis and element-by-element scanning of multiple sites in automatic mode and processing of data in relation to the corresponding observation points [12, 13].

We have applied the SEM method to prove the presence of micro-and macro-quantities of gold and silver, respectively, in the samples of blister copper of copper production.

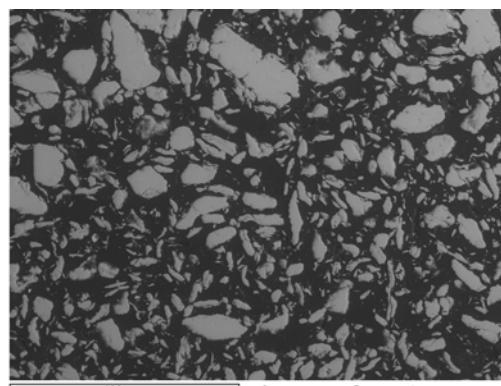


Figure 1. An electronic image of the surface structure of the sample of blister copper

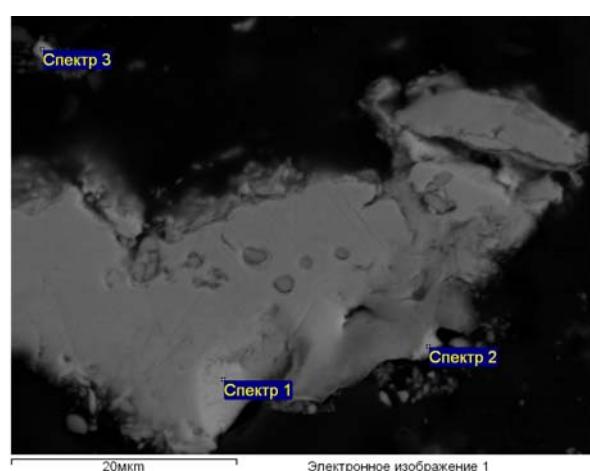


Figure 2. Fragment of SEM image of the surface structure of the sample of blister copper on the impurity content (C, O, Al, Si, Au, Sn, Fe)

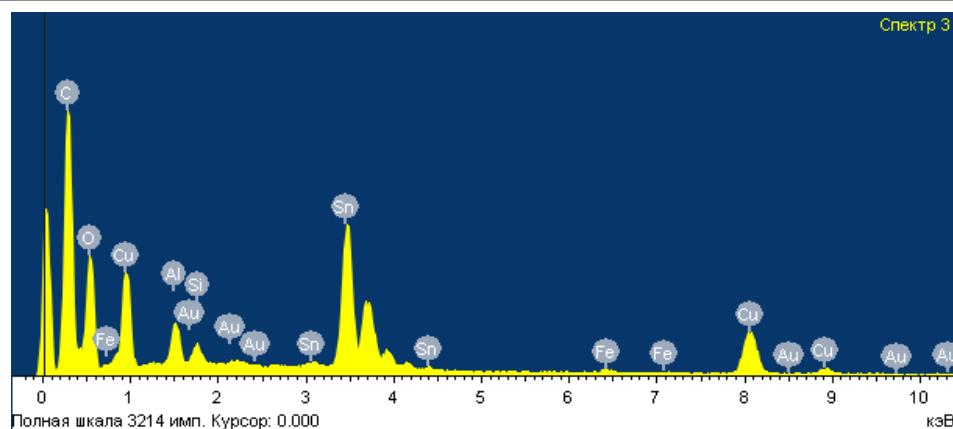


Figure 3 - Spectrum of the analysis site (site №1)

Table 3. Processing parameters of the site №1 for the analysis of all elements (all results in weight %)

Spectrum	O	Al	Si	Fe	Cu	Ag	Sn	Au	Total
Spectrum 1	4.37				95.63				100.00
Spectrum 2	3.85				95.56	0.59			100.00
Spectrum 3	44.29	3.48	1.25	0.74	17.12		32.44	0.66	100.00
Max.	44.29	3.48	1.25	0.74	95.63	0.59	32.44	0.66	
Min.	3.85	3.48	1.25	0.74	17.12	0.59	32.44	0.66	

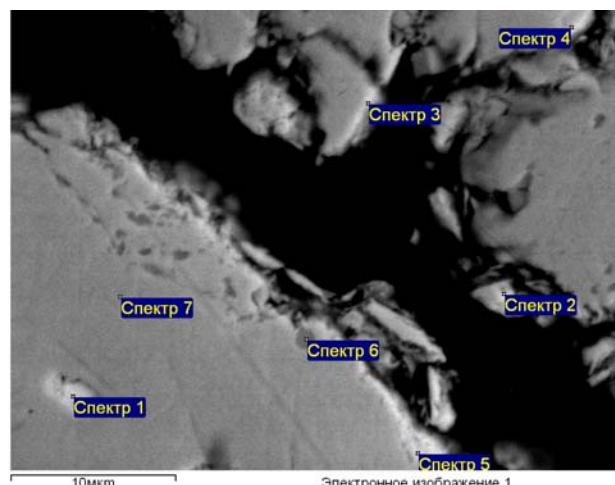


Figure 4 - Fragment of SEM image of the surface structure of the sample of blister copper on the impurity content (C, O, As, Pb, Ag, Sb)

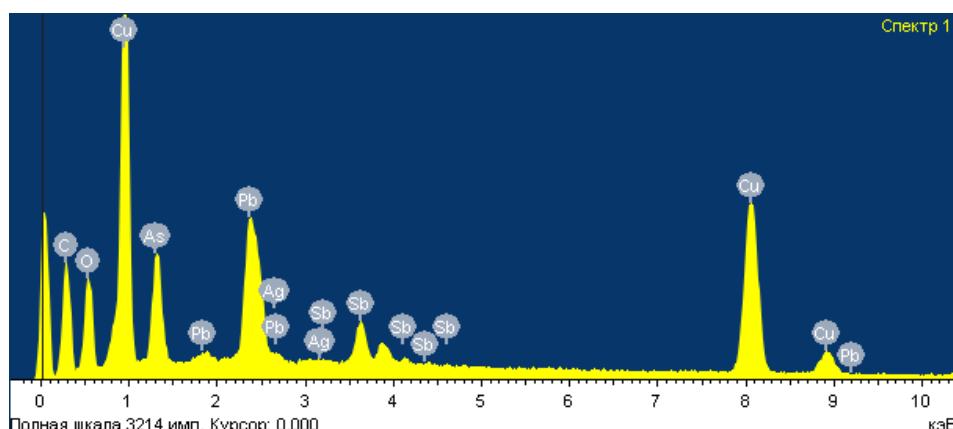


Figure 5 - Spectrum of the analysis site (site №2)

Table 4 - Processing parameters of the site №2 for the analysis of all elements (all results in weight %)

Spectrum	O	Si	Cu	As	Ag	Sb	Pb	Total
Spectrum 1	15.00		41.71	13.94	0.29	7.40	21.67	100.0
Spectrum 2	7.96	0.57	91.47					100.0
Spectrum 3	5.60	1.33	93.06					100.0
Spectrum 4	12.73		62.99	11.92		4.19	8.17	100.0
Max.	15.00	1.33	93.06	13.94	0.29	7.40	21.67	
Min.	5.60	0.57	41.71	11.92	0.29	4.19	8.17	



Figure 6 - A fragment of the SEM image of silver on the surface of the sample of blister copper

Conclusion

Thus, studying of structure surface of samples using SEM we have revealed presence of impurities (C, O, As, Pb, Ag, Sb, Al, Si, Au, Sn, Fe) in blister copper of copper production. Herewith, there was a significant presence of precious metals. So, silver was found in the range of 0.29-0.59%, gold – up to 0.66%.

ӘОК 549:622.775

Р.А. Аубакирова¹, Ж.К. Шоманова², Р.З. Сафаров³, Э. Атасой⁴

¹ Сәрсен Аманжолов атындағы Шығыс Қазақстан мемлекеттік университеті, Өскемен, Қазақстан;

² Павлодар мемлекеттік педагогикалық университеті, Павлодар, Қазақстан;

³ Л. Н. Гумилев атындағы Еуразия ұлттық университеті, Астана, Қазақстан;

⁴ Улудаг Университеті, Бурса, Түркия

ҚҰРАМЫНДА МЫС БАР ӨНІМДЕРДІ АСЫЛ МЕТАЛДАРҒА ТАЛДАУ

Аннотация: Бұл мақалада мыс өндірісінің бастапқы қара мыс үлгілерін электронды-микроскопиялық зерттеу нәтижелері берілген. Асыл металдар – күміс пен алтынның елеулі мөлшері көрсетілген. Нәтижесінде 0.29-0.59% шамасында күміс, 0.66% – ға дейін алтын табылды. Қара мыс үлгілерінде алтын мен күмісті анықтаудың сынамалы-гравиметриялық әдісі сипатталған.

Түйін сөздер: мыс, асыл металдар, балқыту, алтын, күміс, электронды микроскопия, қоспалар.

Р.А. Аубакирова¹, Ж.К. Шоманова², Р.З. Сафаров³, Э. Атасой⁴

¹Восточно-Казахстанский государственный университет имени Сарсена Аманжолова,
Усть-Каменогорск, Казахстан;

²Павлодарский государственный педагогический университет, Павлодар, Казахстан;

³Евразийский национальный университет им. Л.Н. Гумилева, Астана, Казахстан;

⁴Университет Улудаг, Бурса, Турция

АНАЛИЗ МЕДЬ-СОДЕРЖАЩИХ ПРОДУКТОВ НА СОДЕРЖАНИЕ БЛАГОРОДНЫХ МЕТАЛЛОВ

Аннотация: В данной статье представлены результаты электронно-микроскопического исследования образцов черновой меди медного производства. Показано значимое количество благородных металлов – серебра и золота. В результате серебро было обнаружено в пределах 0.29-0.59%, золото – до 0.66%. Описан пробирно-гравиметрический метод обнаружения золота и серебра в образцах черновой меди.

Ключевые слова: медь, благородные металлы, плавление, золото, серебро, электронная микроскопия, примеси.

Information about authors:

Roza Ablakimovna Aubakirova – candidate of chemical sciences, professor of the chemistry department, Sarsen Amanzholov East Kazakhstan State University, roza.aubakirova@bk.ru, <https://orcid.org/0000-0001-9403-1104>

Zhanat Kairollinovna Shomanova – doctor of technical sciences, professor of the Geography and chemistry department, Pavlodar state pedagogical institute, zshoman@yandex.ru, <https://orcid.org/0000-0001-8346-9688>

Ruslan Zairovich Safarov – candidate of chemical sciences, the Acting Associate Professor of the Department of Chemistry, vice-dean in science at Natural Sciences Faculty, L.N. Gumilyov Eurasian national university, ruslanbox@yandex.ru, <https://orcid.org/0000-0003-2158-6330>

Emin Atasoy – doctor of geography, professor, Uludağ Üniversitesi, Eğitim Fakültesi, eatasoy@uludag.edu.tr, <https://orcid.org/0000-0002-6073-6461>

REFERENCES

- [1] Moyano A., Caballero C., Mackay R., Henao H., Itagaki K., Font J. (2006) Arsenic and antimony removal from a complex blister copper. Sohn International Symposium on Advanced Processing of Metals and Materials, San Diego, CA, USA. P.153. (in Eng).
- [2] Czernecki J., Smieszek Z., Giszicki S., Dobrzanski J., Warmuz M. (1998) Problems with elimination of the main impurities in the KGHM Polska Miedz SA copper concentrates from the copper production cycle (shaft furnace process, direct blister smelting in a flash furnace). Symposium on Sulfide Smelting at the 1998 TMS Annual Meeting, San Antonio, TX, USA. P.315. (in Eng).
- [3] Okumura I., Deguti M. (1969). A method for spectrophotometric determination of silver in blister copper, Bunseki Kagaku, 18:651-653. DOI:10.2116/bunsekikagaku.18.651 (in Eng).
- [4] Coursol P., Larouche P. (2004) Using carbonate fluxes to remove oxygen and sulfur from blister copper, JOM: the journal of the Minerals, Metals & Materials Society, 56:42-45. DOI:10.1007/s11837-004-0091-9 (in Eng).
- [5] Busev A.I. (1979) Analytical chemistry of gold [Analiticheskai himia zolota]. Nauka, Moscow, Russia. 264 p. (in Russian).
- [6] Piatneytckii I.V. (1975) Analytical chemistry of silver [Analiticheskai himia serebra]. Nauka, Moscow, Russia. 264 p. (in Russian).
- [7] Iizasa K., Asada A., Mizuno K., Katase F., Lee S., Kojima M., Ogawa N. (2019) Native gold and gold-rich sulfide deposits in a submarine basaltic caldera, Higashi-Aogashima hydrothermal field, Izu-Ogasawara frontal arc, Japan, Miner Deposita, 54(1):117-132. DOI:10.1007/s00126-018-0808-2 (in Eng).
- [8] Nescic B., Cokic S., Budjelan D., Petrovic N. (2001) The determination of the content of gold and silver in geological samples, Journal of the Serbian Chemical Society, 66:45-52. (in Eng).
- [9] Moloughney P.E. (1980) A fire-assay and wet chemical method for the determination of palladium, platinum, gold, and silver in ores and concentrates, Talanta, 27(4):365-367. DOI: 10.1016/0039-9140(80)80097-X (in Eng).
- [10]GOST 15934.10-82. Copper concentrates. Methods for determining gold and silver [Koncentraty medny'e. Metody opredeleniya zolota i serebra]. Moscow, Russia, 1983. (in Russian).
- [11]GOST 31382-2009. Copper. Methods of analysis [Med'. Metody analiza]. Moscow, Russia, 2009. (in Russian)
- [12]Goldstein J.I., Newbury D.E., Michael J.R., Ritchie N.W.M., Scott J.H.J., Joy D.C. (2018) Scanning electron microscopy and x-ray microanalysis, fourth edition. Springer, NY, USA. ISBN: 978-1-4939-6674-5 (Print), 978-1-4939-6676-9 (eBook). DOI: 10.1007/978-1-4939-6676-9 (in Eng).
- [13]Zhou W., Apkarian R., Wang Z.L., Joy D. (2006) Fundamentals of Scanning Electron Microscopy (SEM). In: Zhou W., Wang Z.L. (eds) Scanning Microscopy for Nanotechnology. Springer, New York, NY, USA. ISBN: 978-0-387-33325-0. Online ISBN: 978-0-387-39620-0. DOI:10.1007/978-0-387-39620-0_1 (in Eng).

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации
в журнале смотреть на сайте:

www:nauka-nanrk.kz

<http://chemistry-technology.kz/index.php/en/arhiv>

ISSN 2518-1491 (Online), ISSN 2224-5286 (Print)

Редакторы: *M. С. Ахметова, Т. А. Апендиев, Аленов Д.С.*
Верстка на компьютере *A.M. Кульгинбаевой*

Подписано в печать 05.08.2019.
Формат 60x881/8. Бумага офсетная. Печать – ризограф.
5,25 пл. Тираж 300. Заказ 4.

*Национальная академия наук РК
050010, Алматы, ул. Шевченко, 28, т. 272-13-18, 272-13-19*