

ISSN 2518-1491 (Online),
ISSN 2224-5286 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ

Д.В.Сокольский атындағы «Жанармай,
катализ және электрохимия институты» АҚ

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
АО «Институт топлива, катализа и
электрохимии им. Д.В. Сокольского»

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
JSC «D.V. Sokolsky institute of fuel, catalysis
and electrochemistry»

SERIES
CHEMISTRY AND TECHNOLOGY

1 (439)

JANUARY – FEBRUARY 2020

PUBLISHED SINCE JANUARY 1947

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of chemistry and technologies scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of chemistry and technologies in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of chemical sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Химия және технология сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Химия және технология сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді химиялық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия химии и технологий» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по химическим наукам для нашего сообщества.

Б а с р е д а к т о р ы

х.ғ.д., проф., ҚР ҰҒА академигі
М.Ж. Жұрынов

Р е д а к ц и я а л қ а с ы:

Ағабеков В.Е. проф., академик (Белорус)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Ресей)
Газалиев А.М. проф., академик (Қазақстан)
Ергожин Е.Е. проф., академик (Қазақстан)
Жармағамбетова А.К. проф. (Қазақстан), бас ред. орынбасары
Жоробекова Ш.Ж. проф., академик (Қырғыстан)
Иткулова Ш.С. проф. (Қазақстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Қазақстан)
Баешов А.Б. проф., академик (Қазақстан)
Бүркітбаев М.М. проф., академик (Қазақстан)
Джусипбеков У.Ж. проф. корр.-мүшесі (Қазақстан)
Молдахметов М.З. проф., академик (Қазақстан)
Мансуров З.А. проф. (Қазақстан)
Наурызбаев М.К. проф. (Қазақстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Қазақстан)
Стрельцов Е. проф. (Белорус)
Тәшімов Л.Т. проф., академик (Қазақстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Тәжікстан)
Фарзалиев В. проф., академик (Әзірбайжан)

«ҚР ҰҒА Хабарлары. Химия және технология сериясы».

[ISSN 2518-1491 \(Online\)](#)

[ISSN 2224-5286 \(Print\)](#)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» Республикалық қоғамдық бірлестігі (Алматы қ.)

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №1089-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28; 219, 220 бөл.; тел.: 272-13-19; 272-13-18,
<http://chemistry-technology.kz/index.php/en/arhiv>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2020

Типографияның мекенжайы: «NurNaz GRACE», Алматы қ., Рысқұлов көш., 103.

Главный редактор

д.х.н., проф., академик НАН РК

М. Ж. Журинов

Редакционная коллегия:

Агабеков В.Е. проф., академик (Беларусь)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Россия)
Газалиев А.М. проф., академик (Казахстан)
Ергожин Е.Е. проф., академик (Казахстан)
Жармагамбетова А.К. проф. (Казахстан), зам. гл. ред.
Жоробекова Ш.Ж. проф., академик (Кыргызстан)
Иткулова Ш.С. проф. (Казахстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Казахстан)
Баешов А.Б. проф., академик (Казахстан)
Буркитбаев М.М. проф., академик (Казахстан)
Джусипбеков У.Ж. проф. чл.-корр. (Казахстан)
Мулдахметов М.З. проф., академик (Казахстан)
Мансуров З.А. проф. (Казахстан)
Наурызбаев М.К. проф. (Казахстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Казахстан)
Стрельцов Е. проф. (Беларусь)
Ташимов Л.Т. проф., академик (Казахстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Таджикистан)
Фарзалиев В. проф., академик (Азербайджан)

«Известия НАН РК. Серия химии и технологии».

[ISSN 2518-1491 \(Online\)](#)

[ISSN 2224-5286 \(Print\)](#)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10893-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28; ком. 219, 220; тел. 272-13-19; 272-13-18,

<http://chemistry-technology.kz/index.php/en/arhiv>

© Национальная академия наук Республики Казахстан, 2020

Адрес редакции: 050100, г. Алматы, ул. Кунаева, 142,
Институт органического катализа и электрохимии им. Д. В. Сокольского,
каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Адрес типографии: «NurNaz GRACE», г. Алматы, ул. Рыскулова, 103.

E d i t o r i n c h i e f

doctor of chemistry, professor, academician of NAS RK
M.Zh. Zhurinov

E d i t o r i a l b o a r d:

Agabekov V.Ye. prof., academician (Belarus)
Volkov S.V. prof., academician (Ukraine)
Vorotyntsev M.A. prof., academician (Russia)
Gazaliyev A.M. prof., academician (Kazakhstan)
Yergozhin Ye.Ye. prof., academician (Kazakhstan)
Zharmagambetova A.K. prof. (Kazakhstan), deputy editor in chief
Zhorobekova Sh.Zh. prof., academician (Kyrgyzstan)
Itkulova Sh.S. prof. (Kazakhstan)
Mantashyan A.A. prof., academician (Armenia)
Praliyev K.D. prof., academician (Kazakhstan)
Bayeshov A.B. prof., academician (Kazakhstan)
Burkitbayev M.M. prof., academician (Kazakhstan)
Dzhusipbekov U.Zh. prof., corr. member (Kazakhstan)
Muldakhmetov M.Z. prof., academician (Kazakhstan)
Mansurov Z.A. prof. (Kazakhstan)
Nauryzbayev M.K. prof. (Kazakhstan)
Rudik V. prof., academician (Moldova)
Rakhimov K.D. prof., academician (Kazakhstan)
Streltsov Ye. prof. (Belarus)
Tashimov L.T. prof., academician (Kazakhstan)
Toderash I. prof., academician (Moldova)
Khalikov D.Kh. prof., academician (Tadjikistan)
Farzaliyev V. prof., academician (Azerbaijan)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of chemistry and technology.
[ISSN 2518-1491 \(Online\)](#)

[ISSN 2224-5286 \(Print\)](#)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of Information and Archives of the Ministry of Culture and Information of the Republic of Kazakhstan N 10893-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19; 272-13-18,
<http://chemistry-technology.kz/index.php/en/arhiv>

© National Academy of Sciences of the Republic of Kazakhstan, 2020

Editorial address: Institute of Organic Catalysis and Electrochemistry named after D. V. Sokolsky
142, Kunayev str., of. 310, Almaty, 050100, tel. 291-62-80, fax 291-57-22,
e-mail: orgcat@nursat.kz

Address of printing house: «NurNaz GRACE», 103, Ryskulov str, Almaty.

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES CHEMISTRY AND TECHNOLOGY

ISSN 2224-5286

<https://doi.org/10.32014/2020.2518-1491.13>

Volume 1, Number 439 (2020), 102 – 108

UDC 542.973.7; 547.21

K.A. Shorayeva¹, B.K. Massalimova¹, S.M. Nauryzkulova¹, V.A. Sadykov²

¹M.Kh. Dulaty Taraz State University, Taraz, Kazakhstan;

²Novosibirsk State University, Novosibirsk, Russia;

²Institute of Catalysis named after G.K. Boreskov, Novosibirsk, Russia
k.a.shorayeva@mail.ru

SYNTHESIS OF PILLARED CLAYS FOR USING THEM AS CARRIERS OF CATALYTIC SYSTEMS

Abstract. Natural clays are of particular interest for their rational use as not only adsorbents, but also carriers of new highly selective catalysts. This article presents an overview of the application of pillared clays in catalytic chemistry as catalyst matrix. The physicochemical properties of the synthesized Al-, Zr-, Al / Zr-modified clays were studied by BET, XRF and elemental analysis. The elemental composition of montmorillonite and kaolinite clays was determined. Pillared clays with high specific surface (montmorillonite clay from 20 to 243 m²/g and kaolinite clay from 5 to 66 m²/g.) were obtained. The use of pillared clays in catalysis will help to solve the problems of the development of domestic production of catalysts and the replacement of expensive imported analogues.

Key words: natural clays; montmorillonite; kaolinite; mechanical activation; pillared clay; pillarization.

Introduction

Cost-effective and environmentally friendly catalysts are always in demand for synthesis of valuable organic compounds. The main features of a highly efficient catalytic support are: 1) developed surface area for the location of catalytically active centers [1, 2], 2) high thermal stability to prevent sintering and abrasion of the catalyst [3, 4] 3) the presence of various functional groups responsible for stabilization and activation of the catalytically active phase [5, 6].

The presented requirements are fully met by natural clays with a high specific surface. Obtaining of pillared clays and their modification by various transition metal complexes lead to the formation of new porous structures with unique physicochemical properties [7]. In this regard, the urgent task is to develop catalysts based on pillared clay-matrix both for metals and for metal oxides deposited on the surface as catalytically active phases [8].

Therefore the goal of this study is to synthesize new pillared clay samples for the development of highly selective catalysts and to obtain high yields of industrially important gas and petrochemical products, as well as to study the physicochemical properties of columnar structures based on natural clays of the Tagan and Turgay deposits of the East Kazakhstan region.

Materials and methods

Objects of study - synthesized columnar clays for use as a catalyst carrier. Natural clays of the Tagan and Turgay deposits of East Kazakhstan region were used in this work.

Mechanical activation of natural clays

To activate natural kaolinite clays, the AGO-2 high-voltage planetary mill with steel balls with a diameter of 8 mm and a total mass of 200 g, with 150 ml water-cooled steel drums was used. The ratio of the mass of the balls to the mass of the mixture (M) was 20:30. The rotational speed of the drums is 1200 rpm. To ensure a low level of powder contamination in the steel grinding medium, the natural lining of the working surface of the drums and balls, obtained by preliminary processing of a similar mixture, leading

to coating the surface of the balls and the inner surface of the drums with the processed composition [9], was used.

Synthesis of pillared clays

Natural clays pre-cleaned and ground to a particle size of 0.25 mm were incubated for 24 hours at room temperature for complete hydration. The aluminum and zirconium hydroxocomplexes obtained by hydrolysis of aqueous solutions of aluminum chloride (0.2 M) and zirconium (0.2 M) in an aqueous solution of NaOH (0.5 M) were used as intercalating solutions [7, 8, 10]. Pillarization was carried out by slowly adding an intercalating agent to clay samples and further washing from chlorine ions. The obtained columnar clays were dried for one day at room temperature and then calcined at a temperature of 500°C for 5 hours [11].

Textural and physico-chemical properties of pillared clays

The texture characteristics of pillared clays were studied via nitrogen adsorption and desorption isotherms using the BET method (Brauner-Emmett-Teller) on SORBTOMETR-M device (Russia). The change in the phase composition of columnar clays was monitored using x-ray phase analysis on a general-purpose diffractometer DRON-4-0.7 with CuK α radiation (Russia).

The elemental composition of the pillared clay samples was analyzed using an INCAENERGY energy dispersive spectrophotometer (OXFORDINSTRUMENTS, UK) combined with Superprobe 733 electron probe microanalyzer at an accelerating voltage of 25 kV and a probe current of 25 nA.

Results and discussion

Montmorillonite is known to be a clay composed of blocks of tetrahedral quartz sheets with a central octahedral aluminum oxide sheet with the chemical formula $(\text{Si}_{7,8}\text{Al}_{0,2})^{\text{IV}}(\text{Al}_{3,4}\text{Mg}_{0,6})^{\text{VI}}\text{O}_{20}(\text{OH})_4$, and the theoretical composition without intermediate material is SiO₂ 66.7%, Al₂O₃ 28.3% and H₂O 5%. Taking into account the speciation of various metals in this formula, the theoretical net surface charge on montmorillonite is 0.8 charge / element, which is responsible for the adsorption of cations [12].

Elemental analysis of the oxide composition of natural montmorillonite and kaolinite clays samples was carried out using quantitative X-ray spectral analysis. The results are presented in table 1.

Table 1 - Elemental composition of natural kaolinite and montmorillonite clay samples

Element / Sample	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	TiO ₂	CaO	MgO	K ₂ O	Na ₂ O	PS
Montmorillonite Clay	Elementcontent, wt. %								
	55,5	19,38	4,4	0,3	1,98	2,18	1,5	1,14	9,5
Element / Sample	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	TiO ₂	CaO	MgO	K ₂ O	Na ₂ O	PS
Kaolinite clay	Elementcontent, wt. %								
	39,33	40,20	17,80	2,01	n.e	0,16	n.e	0,19	0,31

Note: PS –

The data presented in Table 1 indicate that the montmorillonite clay sample contains a large number of alkali and alkaline earth metal cations that can participate cation-exchange reactions, while Ca²⁺ and K⁺ ions are absent in the kaolinite clay sample and only small amounts of Mg²⁺ and Na⁺ are detected. The results obtained are consistent with published data [13, 14].

Kaolinite is a clay mineral from the group of aqueous aluminum silicates with a chemical composition: Al₄[Si₄O₁₀](OH)₈. It contains 39.5% Al₂O₃, 46.5% SiO₂ and 14% H₂O. The crystal structure of kaolinite consists of two-layer packets containing one oxygen tetrahedral layer of the composition [Si_{2n}O_{5n}]²ⁿ⁺ and one aluminum-hydroxyl octahedral layer of the composition [Al_{2n}(OH)_{4n}]²ⁿ⁺. Both layers are combined into a package through common oxygen-silicon-oxygen layer. These layers are interconnected by weak bonds, which determine the very perfect cleavage of kaolinite and the possibility of different overlays of one layer onto another.

Considering the speciation of various metals in this formula, the theoretical net surface charge on kaolinite is zero. However, kaolinite acquires a small total negative charge due to the fact that its surface is not completely inert [12-15].

Thus, mechanical activation of kaolinite clay (Turgay deposit, East Kazakhstan area) was carried out on a high-voltage planetary mill AGO-2. Spectra for natural and mechanically activated kaolinite clay, which are shown in Figures 1 and 2, were obtained by the method of diffraction of the total X-ray radiation (DRON-4-0.7).

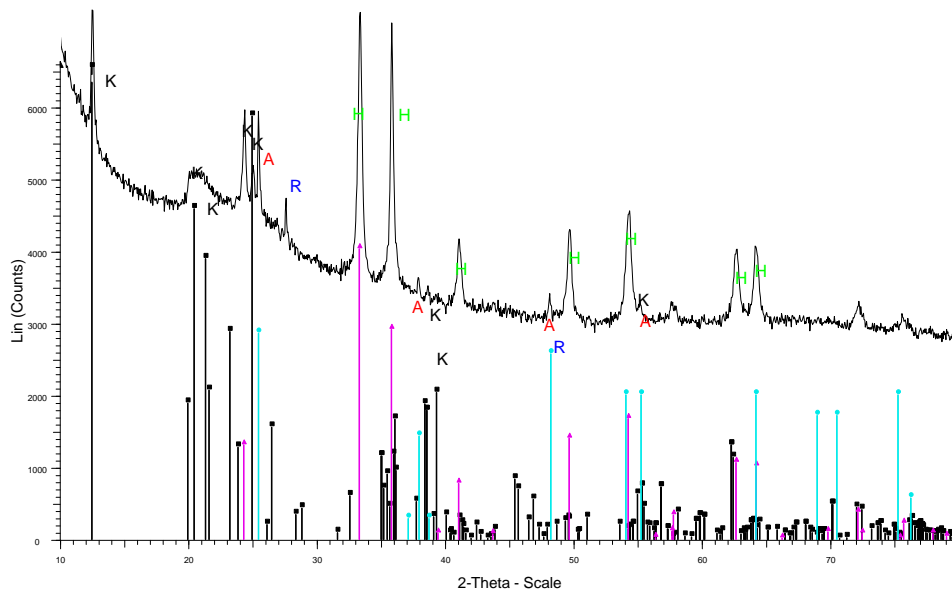


Figure 1 - Diffraction pattern of a sample of the original natural clay: K-kaolinite, A-anatase, R-rutile, H-hematite

When studying the spectrum of a sample of the original natural clay (Figure 1), kaolinite diffraction reflections were recorded (K, PDF-080-0885) with interplanar distances 7.12 ($12.40^\circ 2\theta$), 4.38 (20.35°), 4.16 (21.34°), 3.56 (24.96°) Å; hematite ($\alpha\text{-Fe}_2\text{O}_3$, (PDF-089-8103) with interplanar distances 3.661(24.30°), 2.69 (33.3°), 2.51 (35.78°), 2.198 (41.02°), 1.834 (49.66°), 1.688 (54.30°), 1.598 (57.64°), 1.481 (62.68°), 1.449 (64.18°), 1.308 (72.18°); ($26.85^\circ 2\theta$); TiO_2 (anatase – 3.502 (25.41°), 2.373 (37.88°), 1.89 (49.09°), 1.664 (55.14°); TiO_2 (rutile – 3.240 (27.50°) Å ($^\circ 2\theta$)).

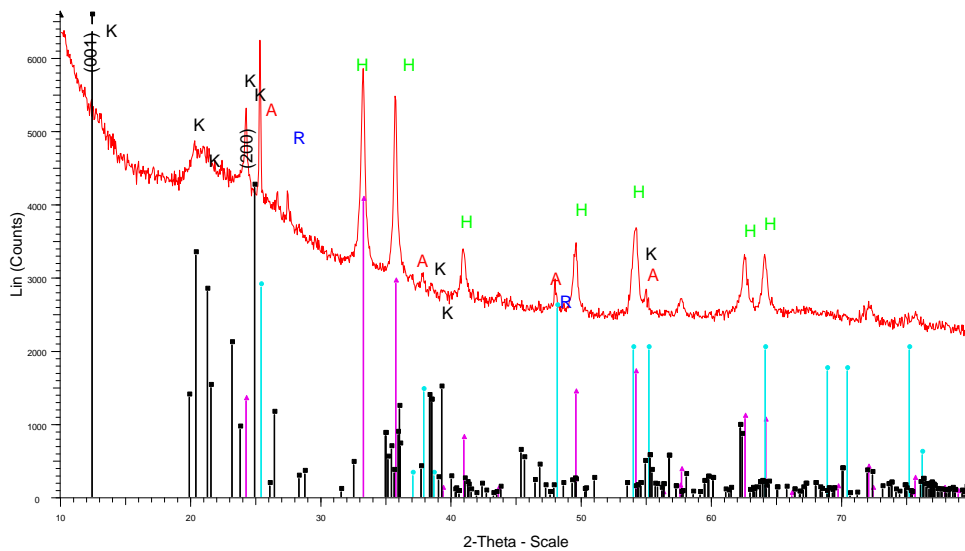


Figure 2 - Diffraction pattern of a sample of modified clay: K-kaolinite, A-anatase, R-rutile, H-hematite

Figure 2 shows the diffraction reflections of mechanically activated kaolinite clay.

According to the literature [15-19], the x-ray spectra of kaolinite clays have nine peaks in the range $1-30^\circ (2\theta)$:

- The basal distance is 7,27 Å ($2\theta = 12,15^\circ$) with intensity 79,4% and tip width 0,20 ($2\theta = 12,15^\circ$);
- Calcined kaolinite gives 13 peaks in the same range 2. The basal distance is 7,15 Å ($2\theta = 12,15^\circ$) with intensity 69,7% for kaolinite and tip width 0,10 ($2\theta = 12,15^\circ$);

- For acid activated kaolinite, the expansion of the basal gap is from 7,27 to 7,30 Å; $2\theta = 12,14^\circ$, and the peak intensity is from 23.14% to 21.32% [16].

According to the data obtained, it can be concluded that after mechanical activation, the phase and chemical composition of kaolinite clay has changed, since kaolinite reflections (001) with interplanar spacings of 7.12 Å ($12.40^\circ 2\theta$) and (002) 3.56 Å ($24.96^\circ 2\theta$) not detected. Hydrogen bonds between the octahedral layer and the oxygen of the tetrahedral layer can serve as a source of interlayer bonds in the structure of kaolinite. [19, 20].

Despite the fact that many works on the general structure of pillared clays have been published, the detailed structure of the columns and the type of connection of the columns with silicate layers are still poorly understood.

Natural clays, including kaolinite and montmorillonite, have a layered structure and high cation exchange capacity. The surface area values vary from 5 to 25 m²/g for kaolinite and 15.5–82.0 m²/g for montmorillonite depending on the particle size distribution, particle shape, and pore distribution in the clay material [20, 21].

Changes in the texture characteristics of pillared montmorillonite and kaolinite clays according to the isotherms of low-temperature nitrogen adsorption are presented in table 2.

Table 2 - Structural characteristics of pillared clays

Type of montmorillonite pillared clay	The content of the oxide columns, wt. %	Specific surface area S_{BET} , m ² /g	Type of kaolinite pillared clay	The content of the oxide columns, wt. %	Specific surface area S_{BET} , m ² /g
MГ-1-Zr/Ba	ZrO ₂ – 23%	243	KГ-1-Zr	ZrO ₂ – 18%	66
MГ-2-Zr/Sr	ZrO ₂ – 22%	240	KГ-2-Al	Al ₂ O ₃ – 15%	55
MГ-3-Zr/Ca	ZrO ₂ – 22.5%	240	KГ-3-Zr/Al	Al ₂ O ₃ – 4%, ZrO ₂ – 18%	51
Note: The specific area of natural montmorillonite clay is ~ 20 m ² /g.			Note: The specific area of natural kaolinite clay is ~ 5 m ² /g.		

The data in table 2 show that the specific surface area of the initial clay increases with pilling: in montmorillonite clay from 20 to 243 m²/g and in kaolinite clay from 5 to 66 m²/g, the content of zirconium reaches 18-23%, aluminum 4 -15%.

The obtained characteristics are in good agreement with the published data that montmorillonite and kaolinite can be used as starting material for modification with the introduction of aluminum and zirconium into the intermediate layers [12–15, 22–24].

The synthesized columnar clays are environmentally friendly and effective for use as carriers in the preparation of heterogeneous catalysts. Also, their use as adsorbents in the production of petrochemical and organic chemicals is not ruled out.

Conclusion

The structure of natural and pillared clays was studied, the relationship between the structure of the pillars and the mechanism of their formation was determined, columnar clays having catalytic properties were obtained.

It is shown that pillared clays synthesized from natural clays of the Tagan and Turgay deposits of the East Kazakhstan region, the Republic of Kazakhstan, can be used as carriers for catalysts. Their specific surface area and catalytic activity are significantly increased by using the pilling process.

Acknowledgments

This work was financially supported by M.Kh. Dulati Taraz State University, Taraz, Kazakhstan. Research work was carried out on the basis of the scientific laboratory of "Chemistry and Chemical Technology" department of TarSU and "Deep Oxidation Catalysts" laboratory of the Boreskov Institute of Catalysis SB RAS, Novosibirsk, Russia.

К.А. Шораева¹, Б.К. Масалимова¹, С.М. Наурызкулова¹, В.А. Садыков²

¹ М.Х. Дулати атындағы Тараз мемлекеттік университеті, 080000, Тараз, Қазақстан;

² Г.К. Боресков атындағы катализ институты, 630090, Новосибир, Ресей

КАТАЛИТИКАЛЫҚ ЖҮЙЕЛЕРДІҢ ТАСЫМАЛДАУШЫСЫ РЕТІНДЕ ҚОЛДАНЫЛАТЫН БАҒАНАЛЫ САЗБАЛШЫҚТАРДЫ СИНТЕЗДЕУ

Аннотация. Табиғи сазбалшықтарды адсорбенттер ретінде ғана емес, сонымен қатар жаңа жоғары селективті катализаторлардың тасымалдаушылары ретінде де ұтымды қолдану үлкен қызығушылық тудырады. Бұл мақалада каталитикалық химия бағытында катализаторлардың тасымалдаушысы ретінде бағаналы сазбалшықтарды қолдануға шолу жасалған. Al-, Zr-, Al/Zr-модификацияланған сазбалшықтардың физика-химиялық қасиеттері элементтік талдау, БЭТ және РФА әдістері арқылы зерттелген.

Каолинитті сазбалшықты механикалық активтендіру (Торғай кен орны, Шығыс Қазақстан облысы) жоғары кернеулі АГО-2 планеталық диірменінде жүзеге асырылды. Жалпы рентген сәулесінің дифракциясы әдісімен (DRON-4-0.7) табиғи және механикалық активтендірілген каолинит сазбалшықтарына арналған спектрлер зерттелді.

Табиғи сазбалшықтан жасалған үлгінің спектрін зерттеу барысында, каолиниттің (K, PDF-080-0885) дифракциялық шағылыстары: 7.12 (12.40 ° 2 θ), 4.38 (20.35), 4.16 (21.34), 3.56 (24.96) Å 3.661 (24.30), 2.69 (33.3), 2.51 (35.78), 2.198 (41.02), 1.834 (49.66), 1.688 (54.30), 1.598 (57.64), гематиттің (α -Fe₂O₃, PDF-089-8103) аралық қабаты: 1.481 (62.68), 1.449 (64.18), 1.308 (72.18); кварц (26,85 ° 2 θ); TiO₂ (анатаза - 3.502 (25.41), 2.373 (37.88), 1.89 (49.09), 1.664 (55.14); TiO₂ (рутил - 3.240 (27.50) Å (° 2 θ) аралық қабаттары жазылды. Алынған мәліметтер негізінде сазбалшықтың фазалық құрамы туралы қорытынды жасауға болады. Каолинит сазбалшығының механикалық құрамы механикалық активацияға байланысты өзгерді, өйткені 7,12 Å (12.40 °2 θ) және (002) 3.56 Å (24.96 °2 θ) аралығындағы қабат кеңістігі бар каолинит (001) шағылыстары анықталмады.

Зерттеуге алынған каолинит және монтмориллонит сазбалшықтарының элементтік құрамдары анықталды. Нәтижесінде монтмориллонит үшін ~20-дан 243 м²/г, каолинит үшін ~5-тен 66 м²/г дейінгі меншікті беттік қабаты бар бағаналы сазбалшықтар алынды.

Алынған көрсеткіштер монтмориллонит пен каолинитті аралық қабаттарға алюминий мен цирконий енгізумен модификациялау үшін бастапқы материал ретінде қолдануға болатыны әдебиеттерде жақсы келісілген.

Осылайша, жоғарыда келтірілген ақпарат синтезделген бағаналы саздар экологиялық таза және гетерогенді катализаторлардың тасымалдаушысы ретінде пайдалану үшін тиімді екенін көрсетті. Катализде аталған бағаналы сазбалшықтарды қолдану катализаторлардың отандық өндірісін дамыту және қымбат импорттық аналогтарын алмастыру мәселесін шешуге септігін тигізеді.

Түйін сөздер: табиғи сазбалшықтар; монтмориллонит; каолинит; механикалық активтендіру; бағаналы сазбалшықтар; бағаналау.

К.А. Шораева¹, Б.К. Масалимова¹, С.М. Наурызкулова¹, В.А. Садыков²

¹ Таразский государственный университет имени М.Х. Дулати, 080000 Тараз, Казахстан;

² Институт катализа имени Г.К. Бореского, 630090 Новосибирск, Россия

СИНТЕЗ СТОЛБЧАТЫХ ГЛИН ДЛЯ ПРИМЕНЕНИЯ ЕГО В КАЧЕСТВЕ НОСИТЕЛЯ КАТАЛИТИЧЕСКИХ СИСТЕМ

Аннотация. Природные глины представляют особый интерес для их рационального использования в качестве не только адсорбентов, но и носителей новых высокоселективных катализаторов. В данной статье представлен обзор сведений использования столбчатых глин в области каталитической химии в качестве носителей катализаторов. Изучены физико-химические свойства синтезированных Al-, Zr-, Al/Zr-модифицированных глин методами БЭТ, РФА и элементного анализа.

Была проведена механическая активация каолиновой глины (Тургайское месторождение, ВКО) на высоконапряженной планетарной мельнице АГО-2. Методом дифракции общего излучения рентгеновских лучей (DRON-4-0.7) были изучены спектры для природной и механически активированной каолиновых глин.

При исследовании спектров образца исходной природной глины были зафиксированы дифракционные рефлексы каолинита (K, PDF-080-0885) с межплоскостными расстояниями 7.12 (12.40° 2 θ), 4.38 (20.35), 4.16 (21.34), 3.56 (24.96) Å; гематита (α -Fe₂O₃, PDF-089-8103) с межплоскостными расстояниями 3.661(24.30), 2.69 (33.3), 2.51 (35.78), 2.198 (41.02), 1.834 (49.66), 1.688 (54.30), 1.598 (57.64), 1.481 (62.68), 1.449 (64.18), 1.308 (72.18); кварца (26.85° 2 θ); TiO₂ (анатаз – 3.502 (25.41), 2.373 (37.88), 1.89 (49.09), 1.664 (55.14); TiO₂ (рутил – 3.240 (27.50) Å (° 2 θ). По полученным данным можно сделать выводы о том, что фазовый состав проведения механической активации химический состав каолиновой глины изменилась, так как, рефлексы каолинита (001) с межплоскостными расстояниями 7.12 Å (12.40° 2 θ) и (002) 3.56 Å (24.96° 2 θ) не обнаружены.

Определены химические элементные составы исследуемых монтмориллонитовой и каолиновой глины. В результате исследования получены столбчатые глины с высокой удельной поверхностью: у монтмориллонитовой глины от ~20 до 243 м²/г и у каолиновой глины от ~5 до 66 м²/г.

Полученные показатели вполне согласуются с литературными данными о том, что монтмориллонит и каолинит вполне могут быть использованы в качестве исходного материала для модификации с введением алюминия и циркония в промежуточные слои.

Таким образом, выше представленные сведения показали, что синтезированные столбчатые глины являются экологически чистыми и эффективными для применения их в качестве носителя гетерогенных катализаторов. Использование столбчатых глин в катализе поможет решить вопросы развития отечественного производства катализаторов и замены дорогих импортных аналогов.

Ключевые слова: природные глины; монтмориллонит; каолинит; механическая активация; столбчатые глины; пилларирование.

Information about authors:

Shorayeva Kamshat Abitkhanovna – 3-year PhD student of specialty chemistry, M.Kh. Dulati Taraz State University, Tole bi str. 60, Taraz, Kazakhstan, k.a.shorayeva@mail.ru, <https://orcid.org/0000-0002-2144-233X>

Massalimova Bakytgul Kabukenovna – candidate of chemical sciences, associated professor, manager of the department of “Chemistry and chemical technology”, M.Kh. Dulati Taraz State University, Tole bi str. 60, Taraz, Kazakhstan, massalimova15@mail.ru, <https://orcid.org/0000-0003-0135-9712>

Naurzkulova Symbat Muratbekovna – 2-year PhD student of specialty chemistry, M.Kh. Dulati Taraz State University, Tole bi str. 60, Taraz, Kazakhstan, simbat_3@mail.ru, altynbekova.1985@inbox.ru, <https://orcid.org/0000-0002-8489-320X>

Sadykov V.A. – doctor of chemical sciences, professor, Boreskov Institute of Catalysis, Novosibirsk, Russia, vasadykov@mail.ru, sadykov@catalysis.ru, <https://orcid.org/0000-0003-2404-0325>

REFERENCES

- [1] Prajitha Prabhakaran M.K., Pushpaletta P. (2017) Preparation of solid acid catalyst from modified Kaolinite and its characterization and catalytic activity, Indian Journal of Chemical Technology, 24:637-643 (in Eng).
- [2] Nikiforova M.A., Rysev A.P., Sadykov T.F., Konkova T.V., Alekhina M.B. (2011) Preparation, texture parameters and catalytic properties of Ce montmorillonite, Advances in chemistry and chemical technology, TomXXV, №8 (124) (in Russ).
- [3] Barantseva S.E., Yakovleva N.S., Poznyak A.I., Nichipor V.N. (2018) Pyrophyllite-kaolinite rocks – a promising raw material for the ceramic industry, Subsoil use issues, 1:82-86(in Russ).
- [4] Dang T., Chen B., Lee D. (2013) Application of kaolin-based catalysts in biodiesel production via transesterification of vegetable oils in excess methanol, Bioresource Technology, 145:175-181. <https://doi.org/10.1016/j.biortech.2012.12.024> (in Eng).
- [5] Adamski A., Legutko P., Dziadek K., Parkhomenko K., Aymonier C., Sadykov V., Roger A. (2018) Role of CeO₂-ZrO₂ Support for Structural, Textural and Functional Properties of Ni-based Catalysts Active in Dry Reforming of Methane, E3S Web of Conferences, Energy and Fuels 2018, <https://doi.org/10.1051/e3sconf/201910802018> (in Eng).
- [6] Rosengart M.I., Vyunova G.M., Isagulyants G.V. (1988) Layered silicates as catalysts, Advances in chemistry, 57, No 2. C:204–227(in Russ).
- [7] Komov D., Nikitina N.V., Kazarinov I.A. (2015) Sorbents based on natural bentonites, modified by polyhydroxocations of iron (III) and aluminum by the sol-gel method, News of Saratov university. 15:27-34(in Russ).
- [8] Konkova T.V., Alekhina M.B. (2012) Modification of bentonite clay for catalytic wastewater treatment from organic impurities, Water: chemistry and ecology, 4:77-81 (in Russ).
- [9] Poluboyarov V.A., Solonenko O.P., Zhdanok A.A., Chesnokov A.E., Paulini I.A. (2017) Comparison of the efficiency of AGO-2 and Activator-2SL mills during mechanical activation of titanium powder, Journal of Siberian Federal University, Engineering and Technologies, 10(5):646-656 (in Russ).

- [10] Gil A., Korili S.A., Vicente A. (2008) Recent Advances in the Control and Characterization of the Porous Structure of Pillared Clay Catalysts, *Catalys. Reviews*, 50:153-226 (in Eng).
- [11] Shadin A.N., Zakarina N.A., Volkova L.D. (2016) Processing weighted vacuum gasoil by cracking on zeolite and HC-Y-containing catalysts supported on aluminum column montmorillonite, *Bulletin of National Academy of sciences of the Republic of Kazakhstan*, 362:111-117 (in Russ).
- [12] Bhattacharyya K. G., Gupta S. S. (2008) Adsorption of a few heavy metals on natural and modified kaolinite and montmorillonite: a review, *Chemistry, Medicine*, 140(2):114-31. DOI:10.1016/j.cis.2007.12.008 (in Eng).
- [13] Jiang M-Q, Jin X-Y, Lu X-Q, Chen Z-L (2010) Adsorption of Pb(II), Cd(II), Ni(II) and Cu(II) onto natural kaolinite clay. *Desalination* 252(1):33–39. <https://doi.org/10.1016/j.desal.2009.11.005> (in Eng).
- [14] Bosco S.M., Jimenez R.S., Vignado C., Fontana J., Geraldo B., Figueiredo F.A., Mandelli D., Carvalho W.A. (2006) Removal of Mn(II) and Cd(II) from wastewaters by natural and modified clays. *Adsorption*, 12(2):133–146 (in Eng).
- [15] Bhattacharyya K.G., Gupta S.S. (2007) Adsorptive accumulation of Cd (II), Co (II), Cu (II), Pb (II), and Ni (II) from water on montmorillonite: Influence of acid activation, *Journal of Colloid and Interface Science*, 310(2):411-424. <https://doi.org/10.1007/s10450-006-0375-1> (in Eng).
- [16] Grim R.E. (1968a) *Clay Mineralogy*, McGraw-Hill, New York, p. 126 (in Eng).
- [17] Grim R.E. (1968b) *Clay Mineralogy*, McGraw-Hill, New York, p. 298.
- [18] Ghosh D., Bhattacharyya K.G. (2002) *Appl. Clay Sci.*, 20:295 (in Eng).
- [19] Bailey S.W. (1988) Chlorites: structures and crystal chemistry. In: *phyllosilicates (exclusive of micas)*, *Rev. Miner.* 19:1 pp.(in Eng).
- [20] Frost R.L. (1997) The structure of the kaolinite minerals – a re-study, *Clay Miner*, 32(1):65-77 (in Eng).
- [21] Chaari I., Medhioub M., Jamoussi F. (2011) Use of clay to remove heavy metals from Jebel Chakir landfill leachate, *Journal of Applied Sciences in Environmental Sanitation* 62:143-148(in Eng).
- [22] Gupta S.S., Bhattacharyya K.G. (2012) Adsorption of heavy metals on kaolinite and montmorillonite: a review, *Phys. Chem. Chem. Phys.*, 14:6698-6723 (in Eng).
- [23] Kalmakhanova M.S., Massalimova B.K., Diaz de Tuest J.L., Gomes H.T., Nurlibaeva A.H. (2018) Novelty pillared clays for the removal of 4-nitrophenol by catalytic wet peroxide oxidation, *News of the national academy of science of the republic of Kazakhstan, series of geology and technical sciences*, 429:12-19 (in Eng).
- [24] Massalimova B.K., Shorayeva K.A., Nauruzkulova S.M., Jetpisbayeva G.D., Altynbekova D.T., Amanzhol Zh.E., Sadykov V.A. (2019) The catalytic oxidation of propan-butane mixture on the hydrogen and hydrogen content compounds, *News of the national academy of science of the republic of Kazakhstan, series chemistry and technology*, 434:21-25(in Eng).

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации
в журнале смотреть на сайте:

www.nauka-nanrk.kz

<http://chemistry-technology.kz/index.php/en/arhiv>

[ISSN 2518-1491 \(Online\)](#), [ISSN 2224-5286 \(Print\)](#)

Редакторы: *М. С. Ахметова, Г. Б. Халидуллаева, Д. С. Аленов*
Верстка на компьютере *А.М. Кульгинбаевой*

Подписано в печать 13.02.2020.

Формат 60x88¹/₈. Бумага офсетная. Печать – ризограф.
7,8 п.л. Тираж 300. Заказ 1.